

Article

Photofermentative Poly-3-Hydroxybutyrate Production by *Rhodopseudomonas* sp. S16-VOGS3 in a Novel Outdoor 70-L Photobioreactor

Pietro Carlozzi ^{1,*}, Maurizia Seggiani ² , Patrizia Cinelli ² , Norma Mallegni ² and Andrea Lazzeri ² 

¹ Institute of Ecosystem Study, National Research Council (CNR), Via Madonna del Piano 10, 50019 Sesto Fiorentino (FI), Italy

² Department of Civil and Industrial Engineering, University of Pisa, Largo Lucio Lazzarino 1, 56122 Pisa, Italy; maurizia.seggiani@unipi.it (M.S.); patrizia.cinelli@diccism.unipi.it (P.C.); norma.mallegni@gmail.com (N.M.); andrea.lazzeri@unipi.it (A.L.)

* Correspondence: p.carlozzi@ise.cnr.it; Tel.: +39-055-522-5962

Received: 26 July 2018; Accepted: 31 August 2018; Published: 3 September 2018



Abstract: In the present study, the performance of a 70 L photobioreactor, operating outdoors, was investigated using a purple bacterial strain as *Rhodopseudomonas* sp. S16-VOGS3 for producing poly-3-hydroxybutyrate (PHB). The novel photobioreactor was equipped with 5 rows L-shaped; the bottom of every row was placed in a stainless-steel tank containing water with controlled temperature. The photofermentation trials were carried out under fed-batch mode and under a semi-continuous regimen using lactic acid as the carbon source. The effect of the irradiance and the carbon/nitrogen ratio on the PHB accumulation was investigated, in order to evaluate the optimal bacterial growth. The results showed the feasibility of the prototype photobioreactor for the production of PHB by *Rhodopseudomonas* sp. S16-VOGS3 under the natural light/dark cycle. During the fed-batch growth (144 h long), the cumulative PHB increased quickly reaching a maximum value of 377 mg/L and decreased to 255 mg/L during the semi-continuous regimen (336 h long).

Keywords: photobioreactor; *Rhodopseudomonas* sp. S16-VOGS3; poly-3-hydroxybutyrate; thermal analysis; C/N ratio

1. Introduction

Global petroleum-based plastic production passed 320 million tons (Mt) worldwide in 2016 and it is expected to double in the next 20 years [1]. The United Nations Environment Program (UNEP) showed that only the 54% of plastic waste went to landfills or recycled but the rest entered the ocean and accumulated as debris every year, representing a global problem for the marine ecosystems [2]. Globally, 5 to 13 Mt of plastics end up in the oceans every year [3]. Better recycling and the replacement of the petrol plastics with bioplastics (BPs), not only compostable but also biodegradable in different natural environments, could be a concrete answer to this serious environmental problem. The biodegradability of BPs in different natural environments, such as soil and marine/fresh water, is a key property that makes their life cycle more eco-sustainable compared to the conventional plastics. Despite the environmental benefits of BPs, their actual worldwide production is only about 1 Mt/y [1] but their demand is continuously growing and, in accordance with the last market data collected by European Bioplastics, the global BP production capacity is expected to increase from around 2 Mt/y in 2017 to around 2.4 Mt/y in 2022, in absence of government support measures, and to higher values with specific government incentives [4]. The main limitations that penalize the BPs market are the competition for the use of renewable materials for the food and energy sectors and their

actual high production costs. Among the BPs available on the market, the polyhydroxyalkanoates (PHAs), polyesters synthesized by numerous bacteria, are attracting great attention due to their thermoplastic properties similar to that of polypropylene (PP), good mechanical properties and excellent biodegradability in various ecosystems such as fresh water, soil, industrial/domestic compost and sea water. PHAs, with poly-3-hydroxybutyrate (PHB) as the simplest and most abundant PHA, are synthesized under stressful conditions by higher plants, bacteria (e.g., *Halobacteriaceae* and *Archea*) and many photosynthetic microorganisms such as purple non-sulfur bacteria (PNSB) or genetically enhanced species of microorganisms [5–7].

Due to bioplastic degradability also in seawater, PHAs are among the most promising candidates for the production of biodegradable items for different industrial applications. It has been estimated that the world demand of PHAs is going to increase from the actual 10,000 to 34,000 tons/y in 2018, corresponding to an average growth of about 28% [8]. Nevertheless, their relatively high cost (7–12 €/kg), compared to traditional petroleum-based plastics and also to other biopolymers such as poly-lactic acid (PLA), has restricted their use only to high-value applications in medical and pharmaceutical sectors, refraining research activity on their use in commodities such as packaging and service items. These high market costs are mainly due to the high costs of used carbon sources (e.g., glucose and sucrose), the low productivity and the low efficiency of extraction process of PHAs from microbial biomasses [9,10]. Consequently, further research must be undertaken by scientists in order to reduce the actual production costs of PHAs and increase their industrial sustainability and commercialization. Also, the integration of the PHA production with biorefineries can represent a strategy to lower the actual production costs using the biorefinery by-products (crude glycerol, waste plant oils and low-grade biodiesels) as low-cost substrates for the PHA producing microorganisms [11]. The integrated biorefineries will lead to a new way to produce bioplastics along with biofuels (second generation bioethanol and biodiesel), like the modern oil-based refineries. PHA production processes by means of numerous bacteria (e.g., *Cupriavidus necator*, *Pseudomonas* sp. K, *Ralstonia eutropha* JMP 134 and genera of *Bacillus* sp.) are more studied and known than photosynthetic processes carried out by means of cyanobacteria (*Synechocystis* sp. PCC 6803, *Spirulina platensis* etc.) and/or PNSB (e.g., *Rhodobacter sphaeroides*, *Rhodospirillum rubrum*, *Rhodopseudomonas palustris* etc.). This last family of proteobacteria (*Rhodospirillaceae*) can produce PHA through the photo-fermentation process. The PNSB show a high potential to accumulate intracellular PHB granules as energy and carbon reserves and are active H₂ producers when they are grown under stress conditions [12,13]. Combined production of PHB and bio-hydrogen through photoautotrophic metabolism could lead to a further advantage for the environment by converting solar energy into alternative sources of energy and bioplastics [13]. *Rhodobacter sphaeroides* RV and *Rhodospirillum rubrum* represent the bacterial genera more able to accumulate large quantity of PHB, showing that the efficiency of the biochemical pathway depends not only on the particular species but also on the growth conditions (e.g., some nutrient deficiency and pH value). Knowledge of the mechanism of the aforementioned relationships may provide a clue to an alternative approach of controlling cultivation to achieve the preferred product, PHB or H₂. Khatipov et al. [13] achieved high PHB content (40% of dry cell weight) into the cells of *Rhodobacter sphaeroides* RV on lactate media increasing the initial pH of the ammonium-free medium to 10 or higher.

In the biological PHB production by photo-fermentative process, the photobioreactors must be designed to have an optimal use and penetration of light, these factors are essential to obtain high biomass growth rates and consequent high PHB productivity. In conventional photobioreactors, the increase of the concentration of cells and products and/or the formation of biofilm on the reactor surface tend to markedly reduce the intensity of light [14] with consequent productivity reduction over the time.

In this study, a wild strain of *Rhodopseudomonas* sp. S16-VOGS3, previously selected as PHB-producer [15], was used for producing PHB in a novel outdoor L-shaped row photobioreactor (L-SRP), under the natural light/dark cycle. The photo-fermentation trial was initially carried out

in batch mode and then semi-continuous mode, using lactic acid as carbon source. The aim of this study was to evaluate the performance of the novel photobioreactor in terms of biomass growth and PHB accumulation under the natural sunlight conditions and to investigate the effect of the irradiance (direct and diffuse) and carbon/nitrogen (C/N) ratio. The extracted PHB from *Rhodospseudomonas* lyophilized-biomass produced was characterized in terms of thermal properties and stability in view of its use as thermoplastic polymer.

2. Materials and Methods

2.1. Photobioreactor

The photo of the L-shaped row photobioreactor (L-SRP) used for the photofermentative PHB production is reported in Figure 1a. It is equipped with 5 parallel rows (Pyrex[®] glass make) and the total working volume is 70 L. Every row is a L-shaped loop with 4-pipes laid horizontally in a stainless-steel tank that contains demineralized water at controlled temperature and 8-pipes placed one over the other and connected with U fittings as shown in the Figure 1a. The photobioreactor configuration with the 5 L-shaped loops permitted a good culture temperature control realized by the 4 pipes of each loop submerged in water, reducing the temperature excursion range experienced by bacterial cells. This solution avoided the use of an external refrigeration system.

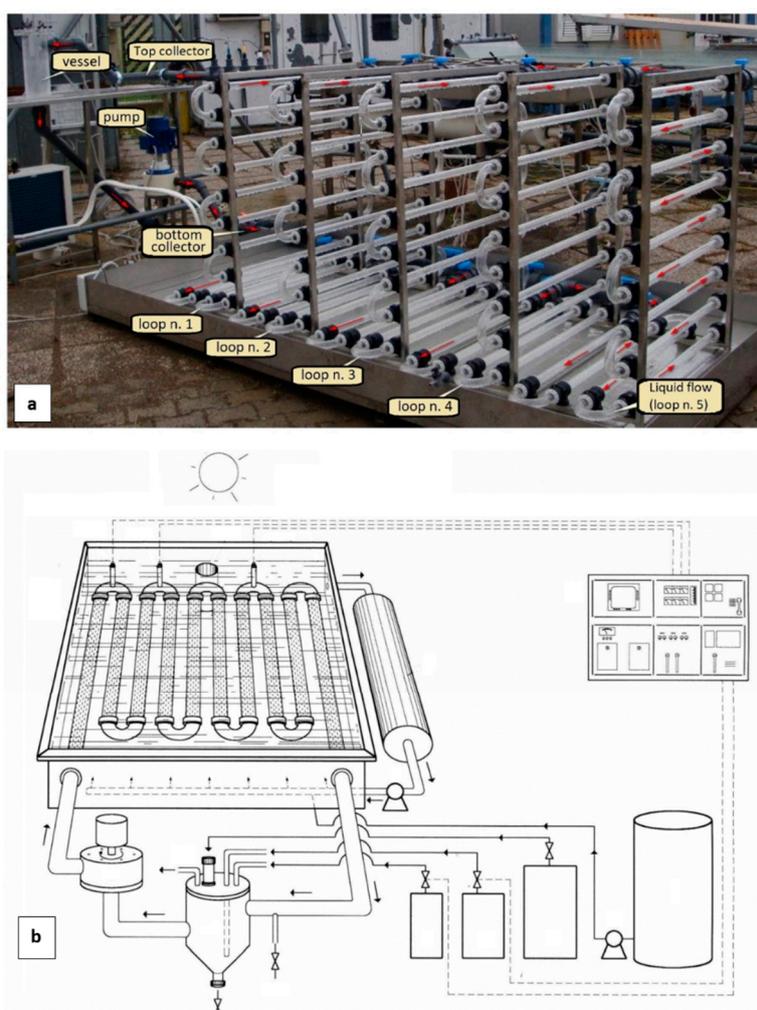


Figure 1. (a) Photo of the novel L-shaped row photobioreactor (L-SRP) operating outdoors for growing *Rhodospseudomonas* sp. S16-VOGS3; (b) Schematic diagram of a previous underwater tubular photobioreactor (UWTP) used for growing *Rhodospseudomonas palustris* 42OL [16,17].

The pipes and U-fittings have inner and outer diameter of 2.6 and 3.0 cm, respectively. All 5 rows are connected with 2 collectors: the first placed at the bottom and the second on the top of the culture system. The photobioreactor is joined with a vessel. A pump, provided with 3 flat blades placed at 120° to one another on the propeller shaft, is used to recirculate the culture in the system: the culture flows into the bottom collector which has 5 pots: one for each loop, then from the bottom up along each line until reaching the top collector. From the top collector, the culture returns to the vessel, where the pH is regulated at 7.0 ± 0.5 by adding 0.5mM HCl. The photobioreactor used in the present work derives from previous studies [16,17] on temperature controlled underwater tubular photobioreactor (Figure 1b) operating in outdoor conditions to growth *Rhodospseudomonas palustris* 42OL.

2.2. Microorganism Strain and Culture Conditions

In the present study, *Rhodospseudomonas* sp. S16-VOGS3, belonging to the culture collection of the Istituto per lo Studio degli Ecosistemi (Consiglio Nazionale delle Ricerche (ISE, CNR), Florence, Italy), was employed. The 16S sequence of *Rhodospseudomonas* sp. S16-VOGS3 was deposited in GenBank under the following accession numbers: KU899101-KU899105.

Rhodospseudomonas sp. S16-VOGS3 cells were grown initially indoors and, then, outdoors in the 70-L photobioreactor. The bacterium was cultured in batch mode into 8-Sovirel bottles containing 100 mL medium at constant temperature of 30 ± 0.2 °C under continuous artificial irradiance of 75 W/m^2 in anaerobic conditions. After 7 days of growth, *Rhodospseudomonas* cells were harvested by centrifugation (9000 rpm) and transferred into two photobioreactors with 4 L working volume (not shown here) containing fresh medium. The growing conditions were the following: fed-batch mode, continuous irradiance of 150 W/m^2 , constant temperature (30 ± 0.2 °C) and anaerobic conditions obtained by fluxing argon (99.99% pure). A 150 W OSRAM power-star HQI-TS lamp was used to light the culture; the light intensity was measured using a Quantum/Radiometer/Photometer. Successively, cells of *Rhodospseudomonas* sp. S16-VOGS3 were used to inoculate the 70 L photobioreactor positioned outdoors containing fresh medium. A total of 1L of growth medium used for both indoor and outdoor bacterial growth contained 4.0 g lactic acid, 0.5 g NH_4Cl , 1.0 g KH_2PO_4 , 0.4 g NaCl, 0.05g $\text{CaCl}_2 \cdot 2\text{H}_2\text{O}$, 0.4 g $\text{MgSO}_4 \cdot 7\text{H}_2\text{O}$, g 0.005 ferric citrate and 0.1 mg para-aminobenzoic acid. Trace elements were provided by adding 10 mL (per 1 L) of a solution containing 30 mg H_3BO_3 , 3.0 mg $\text{MnCl}_2 \cdot 4\text{H}_2\text{O}$, 500 mg $\text{Na}_2\text{MoO}_4 \cdot 2\text{H}_2\text{O}$, 10 mg $\text{ZnSO}_4 \cdot 7\text{H}_2\text{O}$, 1.0 mg $\text{CuCl}_2 \cdot 2\text{H}_2\text{O}$, 2.0 mg $\text{NiCl}_2 \cdot 6\text{H}_2\text{O}$ and 24.5 mg $\text{CoNO}_3 \cdot 6\text{H}_2\text{O}$. The pH of the medium was adjusted to 6.8 by using NaOH solution. During the outdoor bacterial growth, the pH was adjusted by adding HCl solution.

2.3. Outdoor Bacterial Growth

The L-SRP was inoculated in the evening by using the total volume of *Rhodospseudomonas* sp. S16-VOGS3 culture grown indoors. No argon was used for obtaining the anaerobic conditions since these conditions were reached two hours and half after the inoculation due to the dark natural conditions. The L-SRP was operated under fed-batch (FB) mode along the 144 h of biomass growth. A second experiment was carried out under a semi-continuous (SC) regimen, adopted to maintain the cell dry-weight concentration (CDWC) of about 4.0 g/L. Moreover, the medium replacement was accomplished every time (culture time of 72 h) adding to the culture an adequate amount of lactic acid to restore its initial concentration of 4.0 g/L. In this way, the unsuitable situation that could have stopped growth of *Rhodospseudomonas* sp. S16-VOGS3 due to lack of nutrients, such as the carbon source, is avoided. The culture samples were collected through a sampling point with respect to time to measure the CDWC, residual substrate (lactic acid) concentration and intracellular PHB concentrations in accordance with the analytic methods reported below. The investigation was carried out under the natural light/dark cycle in the summer period: 27 June–18 July 2017 at Sesto Fiorentino (Florence, Italy) (Latitude: $43^\circ 49' 54''$ N; Longitude: $11^\circ 11' 57''$ E; Altitude above sea level: 60 m).

2.4. PHB Recovery

Bacterial cells were separated from culture suspension by centrifugation at 9000 rpm and, then, the pellet was suspended in a physiological solution (9‰) to wash it and, then, the suspension was centrifuged at 9000 rpm. The washing operation was repeated twice before collecting the final biomass that was frozen and, then, lyophilized to be used for the subsequent PHB extraction. The extraction was carried out in accordance with Al-Kaddo et al. [18]: about 2 g of lyophilized cells were added to 200 mL of chloroform (CHCl₃) and the suspension was kept under stirring at room temperature for 6 days. Thereafter, the solution was filtered under vacuum utilizing a paper filter (Whatman No. 3) to remove cell debris and the filtrate was concentrated in a rotary evaporator to around 25 mL and PHB was precipitate by addition of 200 mL of cold methanol under vigorous stirring. Wet PHB was collected by centrifugation and then it was air dried, weighted and used for the thermal analyses.

2.5. Analytical Methods

Cell dry-weight concentration (CDWC) and bacteriochlorophyll (Bchl) concentration were determined in accordance with Carlozzi and Sacchi [16]. The PHB content accumulated in the bacterial cells was measured by HPLC (High-Performance Liquid Chromatography) using the Thermo Finnigan-Spectra System 6000 LP (ThermoFinnigan, San José, CA, USA), following the procedure reported elsewhere [15]. The organic acid concentration in the bacteria cultures was determined as reported elsewhere [19] by using the HPLC (Thermo Finnigan-Spectra System 6000 LP) with a C18 analytical column (250 × 4.6 mm) operating at 25 °C. The cells were separated from the culture suspension by disposable syringe filter units (MFS-13 mm, pore size 0.45 µm) and the supernatant sample was injected into the C18 analytical column for the analysis of the lactic acid concentration. An aqueous solution 0.1 wt.% H₃PO₄ was used as the mobile phase at a flow rate of 1.0 mL/min. All analyses were carried out in triplicate.

2.6. Thermal Analysis

Differential scanning calorimetry (DSC) and thermo-gravimetric analysis (TGA) were used to study the thermal properties of the recovered PHB in view of its use as thermoplastic polymer. DSC was performed using a DSC Q200 (TA Instruments, Waters LLC, New Castle, DE, USA) calibrated with standard indium. PHB samples (about 12 mg) were first heated from ambient temperature to 200 °C at a heating rate of 10 °C/min in order to erase any previous thermal history. After an isotherm at 200 °C for 5 min, the samples were cooled until ambient temperature and heated again to 200 °C with an increasing temperature rate of 10 °C/min. The glass transition temperature (T_g), melting temperature (T_m) and enthalpy (ΔH_m) were determined from the second heating thermogram. The degree of crystallinity x_c of PHB was calculated using the following equations:

$$x_c = \Delta H_m / \Delta H_{m,100} \cdot 100$$

where ΔH_m is the melting enthalpy of the sample (J/g); ΔH_{m,100} is the enthalpy value for a theoretically 100% crystalline PHB (146 J/g) [20].

The thermal stability of the polymeric samples produced by *Rhodospseudomonas* sp. S16-VOGS3 was determined by TGA using a TA Q-500 (TA Instruments, Waters LLC, New Castle, DE (USA)). About 10 mg of sample was loaded into an aluminum pan and heated from room temperature to 600 °C at a heating rate of 10 °C/min under nitrogen atmosphere. The thermal stability of the polymer was determined measuring the decomposition temperature (T_d), defined as a temperature corresponding to a sample weight loss of 5%.

3. Results and Discussion

3.1. Photobioreactor Performance

The improved geometry configuration of the novel L-SRP tested in the present study is evident and significant respect to some typical horizontal tubular photobioreactors. The verticalization of the cultural system allows the light to reach full pipe surface. In accordance with a previous investigation [21], spacing properly the rows of the 70-L photobioreactor, the light distribution improved inside *Rhodospseudomonas* culture causing a type of culture lamination that permitted the dilution of solar radiation (SR). In fact, the lamination of the culture can increase the irradiated surface (Si) and consequently the Si/V ratio of the photobioreactor and control the photic ratio by spacing or narrowing the parallel rows. Table 1 shows the internal diameter (di) and the Si/V ratio of several tubular photobioreactors proposed in literature [17,21–24]: the lower the internal diameter the higher the Si/V ratio. With a di of 0.010 m, a Si/V ratio of 400 m⁻¹ was reached [24]. A recent tubular photobioreactor with a Si/V ratio of 182 m⁻¹ was identified as the best culture system among those tested by Palamae et al. [23]. They reported that the Si/V ratio affects the production of biomass and hydrogen differently: a high Si/V ratio favored the hydrogen production over biomass production when growing *Rhodobacter sphaeroides* S10.

Table 1. Internal pipe diameter (di) and some important parameters of tubular photobioreactors proposed in literature.

| di (cm) | Working Volume (L) | Si (m ²) | Si/V Ratio (m ⁻¹) | Ref. |
|---------|--------------------|----------------------|-------------------------------|------------|
| 8.0 | 80.0 | 3.200 | 40.0 | [22] |
| 4.8 | 53.0 | 3.014 | 56.9 | [17] |
| 2.6 | 70.0 | 6.300 | 90.0 | This study |
| 2.2 | 1.0 | 0.182 | 181.7 | [23] |
| 1.6 | 22.1 | 2.200 | 99.5 | [24] |
| 1.0 | 11.0 | 4.400 | 400.0 | [21] |

3.2. PHB Production

Figure 2 shows the profiles of the daily maximum irradiance (I_{max}) and solar irradiation (SR) and Bchl, lactate and PHB concentrations in the bacterial culture during the cultivation of *Rhodospseudomonas* sp. S16-VOGS3 in the outdoor L-SRP under fed-batch mode (run1). After a lag-phase growth period, lasted about 48 h, during which Bchl concentration was stable and the irradiance had a fluctuating behavior (Figure 2a,b), it was observed a continuous increase of the Bchl amount up to double its concentration (3.8 g/L_{culture}) in the subsequent 96 h. During the fed-batch growth (lasted 144 h), lactic acid was consumed and, consequently, added twice (after 72 and 124 h) to restore its initial concentration to 4 g/L (Figure 2c). The lactate concentration restoring operations caused significant heightening of the C/N ratio in the medium since the concentration of ammonia nitrogen (NH₃-N) in the culture broth decreased progressively over time (Figure 2c). It is known that stressed growth conditions caused by a high C/N ratio and/or nutrient limitation (e.g., Nitrogen and Phosphorus) in the culture medium promote the accumulation of intracellular PHB [25–28]. As expected, the PHB concentration in the culture grew over time and, more significantly, when the initial lactate concentration was restored (Figure 2d). In particular, PHB concentration augmented of 32% in the last period of bacterial growth when the amount of NH₃-N was totally depleted and the growth occurred under nitrogen starvation. After 144 h of batch cultivation, a final amount of 377 mg(PHB)/L_{culture} was reached corresponding to a PHB volumetric productivity of about 63 mg L⁻¹ day⁻¹. Recently, a PHB production of 10.3 mg/L/day was reported by growing (indoors) *Synechocystis* PCC6803 [29]. In the present investigation, at the end of *Rhodospseudomonas* sp. S16-VOGS3 fed-batch growth (run 1), the CDWC was 2.92 g/L, which corresponded to the total dry

biomass produced of 134.4 g with the 70 L photobioreactor; the content of PHB in the dry-biomass was $\geq 19.6\%$.

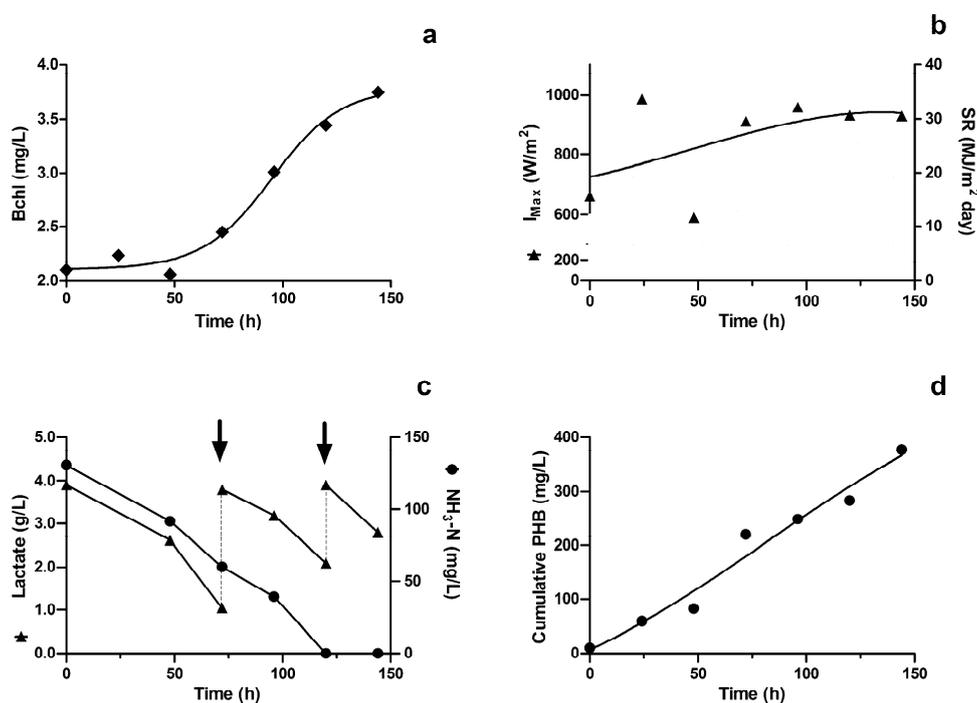


Figure 2. Culture of *Rhodopseudomonas* sp. S16-VOGS3 grown outdoors into a 70 L L-SRP under fed-batch mode (run 1): (a) Bchl concentration versus time, (b) daily changes of the maximum irradiance (I_{Max}) and solar radiation (SR); (c) lactate and ammonia nitrogen (NH_3-N) concentrations versus time and (d) intracellular poly-3-hydroxybutyrate (PHB) concentration. The arrows indicate the points of addition of lactic acid to restore the initial lactate concentration (4 g/L).

In order to evaluate the effect of the solar light intensity on the productivity of PHB accumulated in the bacterial cells, a further investigation was carried out by covering about 80% of the photobioreactor with a dark cloth as shown in Figure 3a (run 2). In this way, the light intensity impinging on the L-SRP was significantly reduced and the culture was irradiated principally by diffuse irradiance, with the exception of the U-fittings. Figure 3b shows typical daily trends of the direct and diffuse irradiance on a horizontal plane measured at Sesto Fiorentino (Florence, Italy) in the period June–July 2017. The results obtained during the 336 h of *Rhodopseudomonas* growth under diffuse radiation (run 2) are shown in Figure 4a–d. During the first 192 h, the photobioreactor was operated in FB mode; when the Bchl concentration reached the value of 16.4 mg/L_{culture} and the CDWC 4.0 g/L, the regimen of growth was changed from FB to SC mode (Figure 4a). In order to maintain the CDWC ranging from 3.2 to 4.1 g/L, an appropriate culture volume was withdrawn from the reactor and replaced with an equal volume of fresh medium every 72 h. During the 336 h of cultivation, the maximum light intensity was quite constant and ranged from 900 to 956 W/m²; on the contrary, the global solar radiation (SR) changed significantly from 22.3 to 29.8 MJ/m² day, as shown in Figure 4b. The lowest reached lactate content was about 1.0 g/L and its initial concentration (4.0 g/L) was restored when the fresh culture medium was added in accordance with the SC regimen of growth (Figure 4c). The NH_3-N amount decreased progressively and reached zero after 164 h of cultivation. The accumulated PHB concentration decreased significantly during the first period of bacterial growth; subsequently, in the SC regimen the PHB concentration ranged from a minimum of 154 to a maximum of 286 mg/L (Figure 4d). This second outdoor investigation demonstrated that when *Rhodopseudomonas* sp. S16-VOGS3 was cultured under lower irradiance, the amount of PHB into bacterial cells decreased significantly, indicating the dominant

role of irradiance on other parameters such as C/N ratio. In fact, as elsewhere demonstrated [27,28], stressed growth conditions caused by high C/N ratios should increase the amount of PHB into bacterial cells, but this was true as far as the results of our first investigation (run 1) is concerned, but not for those of the second one (run 2) (Figure 5). In fact, despite the similar increases in the C/N ratio for both cases (Figure 5a), the PHB content into the cells had an opposite behavior (Figure 5b): during the run 1 (direct irradiance), the PHB content rapidly increased reaching the value of 19.6% of dry biomass weight; during the run 2 (diffuse irradiance), the PHB content decreased reaching a value of about 7% at the end of the investigation.

Recently, the same bacterial strain used in the present study (*Rhodospseudomonas* sp. S16-VOGS3) was identified as a potential candidate for employing crude glycerol coming from biodiesel industry [15]. The authors obtained (indoors) a PHB-rich biomass with a content of 18% on dry-weight biomass, demonstrating that a degradable plastic material as PHB could be efficiently produced by feeding *Rhodospseudomonas* sp. S16-VOGS3 with the byproduct coming from biodiesel industry, in order to obtain a significant reduction of PHB production-costs. A higher cost reduction for PHB production could be achieved when PHB biosynthesis is achieved by CO₂ bioconversion, which is a sustainable alternative to the non-renewable, petroleum-based polymer production [29]. The authors reported a cumulative PHB of about 290 mg/L, along 28 days of *Synechocystis* PCC6803 batch growth. In the present investigation, a similar cumulative PHB-value (286 mg/L) was obtained with *Rhodospseudomonas* sp. S16-VOGS3 grown outdoors during the semi-continuous regimen. An overview of the current carbon sources (e.g., industrial byproducts) used in the PHA production has recently reported by Jiang et al. [11]; they also reported the typical microorganisms that can use the various substrates.

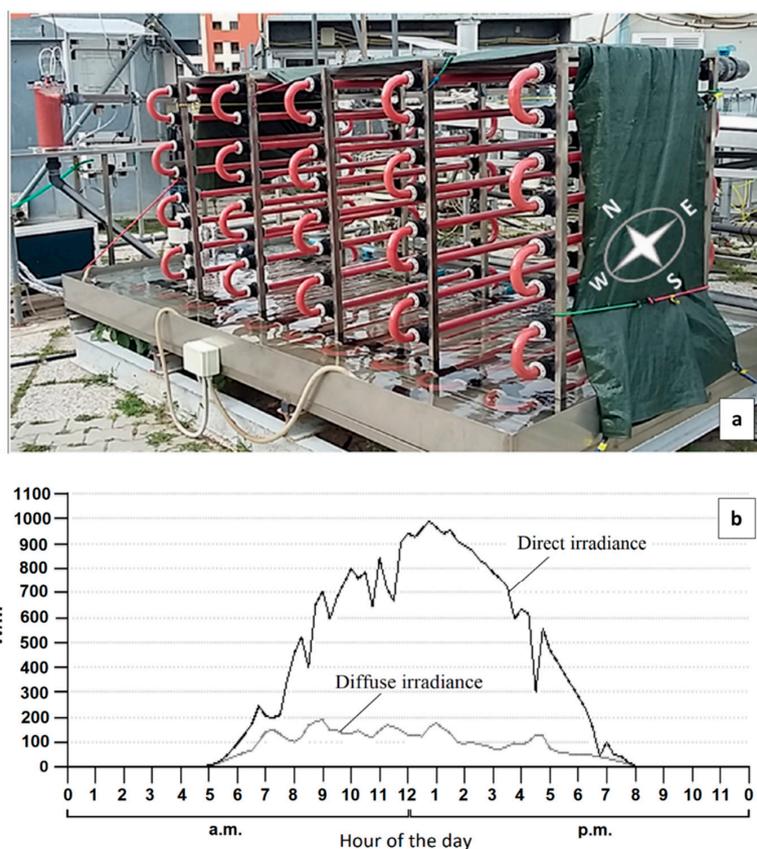


Figure 3. (a) L-shaped row photobioreactor covered with a dark cloth to operate under diffuse irradiance; (b) Average daily trends of direct and diffuse solar irradiance observed at Sesto Fiorentino (Florence, Italy) in June–July/2017.

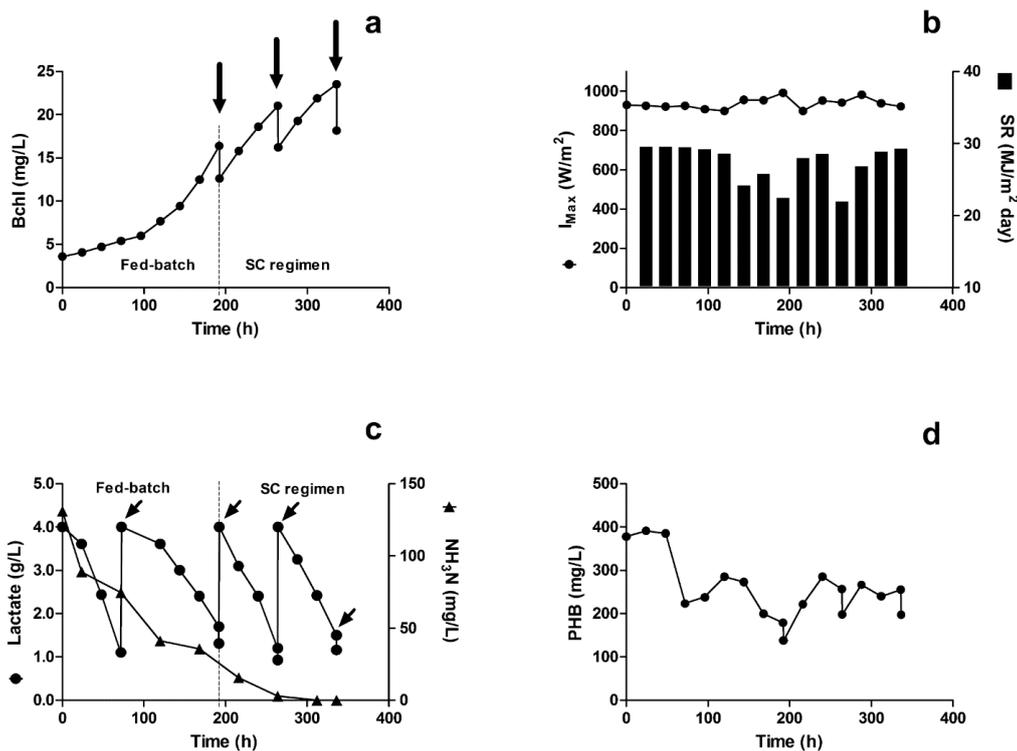


Figure 4. Growth of *Rhodospseudomonas* sp. S16-VOGS3 under fed-batch mode (lasted 192 h) followed by a semi-continuous (SC) regimen (run 2): (a) Bchl concentration versus time, arrows indicate culture dilution times; (b) Changes of IMax and SR versus time; (c) Lactate and ammonia nitrogen concentrations versus time; (d) Intracellular PHB concentration versus time. Arrows indicate the times at which the initial lactate concentration was restored.

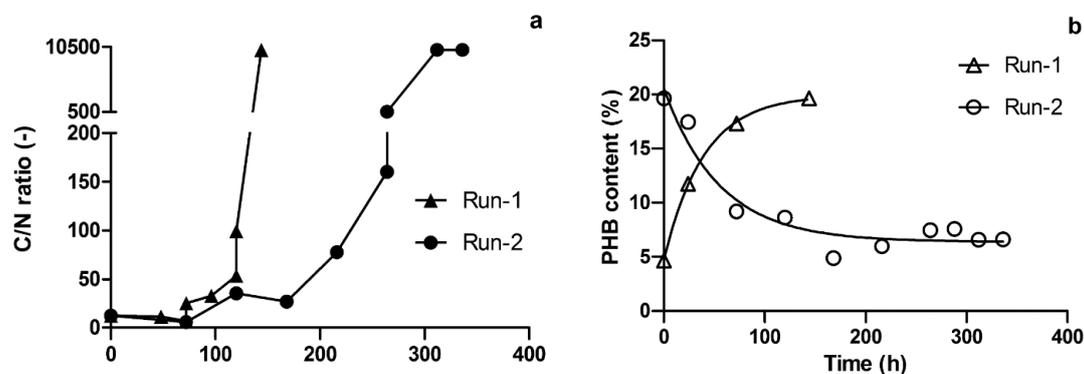


Figure 5. (a) Increase of C/N ratio in the bacterial culture versus time and (b) PHB content into *Rhodospseudomonas* cells grown under fed-batch mode (run 1) and semi-continuous regimen (run 2).

3.3. PHB Thermal Properties and Stability

Figure 6a,b show the DSC and TG/DTG (thermogravimetric and derivate thermogravimetric) thermograms of the recovered PHB from *Rhodospseudomonas* sp. S16-VOGS3 cells, respectively. The DSC thermogram (second heating curve after cooling from the melt) shows an endothermal baseline shift associated with the glass transition ($T_g = 4.2$ °C) followed by a cold-crystallization exotherm ($T_c = 52.8$ °C) and, then, by a melting endotherm ($T_m = 172$ °C). On the basis of the melting enthalpy of the sample, a PHB crystallinity of 51% was evaluated. These results are in excellent accordance with the results of Martino et al. [30] obtained for PHB produced by cultivation of *Cupriavidus necator* DSM 428, using cooking oil as carbon source, and recovered by an enzymatic and chemically assisted

procedure and to those of PHB synthesized by another purple bacteria (*Rhodococcus equi*) investigated by Altaee et al. [31]. Good accordance was obtained also with the results obtained with *Bacillus sphaericus* NII 0838 by Sindhu et al. [32]. The TG and DTG curves of PHB produced with *Rhodopseudomonas* sp. S16-VOGS3 (Figure 6b) show a decomposition temperature (T_d) of 248 °C exhibiting a single weight loss with maximum degradation rate at T_{max} of 262 °C. Similar results were reported by Martino et al. [30] for the PHB produced with *Cupriavidus necator* DSM 428. In Table 2, the thermal properties and stability of the PHB produced in the present study by *Rhodopseudomonas* sp. S16-VOGS3 are compared with those of PHB produced by another purple bacterial strain (*Rhodococcus equi*) [31]. As shown, the thermal properties are very similar, except a lower crystallinity (51% vs. 62%) and T_d of PHB obtained in this study.

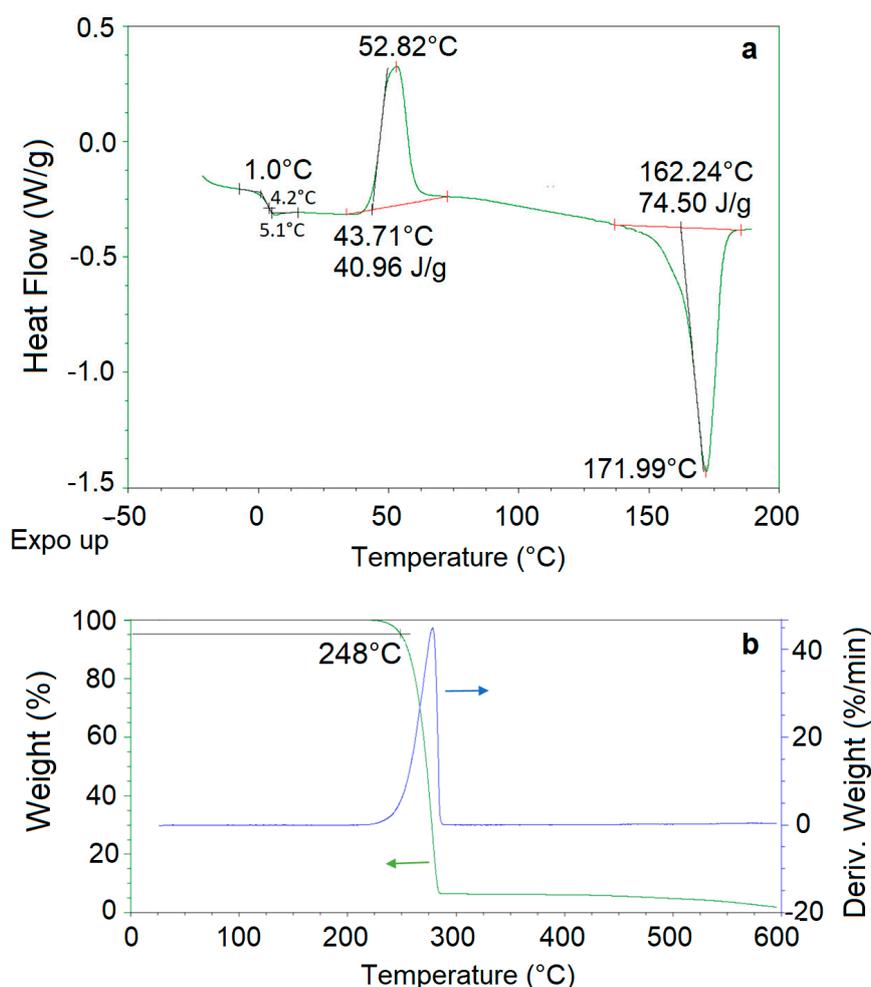


Figure 6. (a) Differential scanning calorimetry (DSC) and (b) thermogravimetric (TG) and derivate thermogravimetric (DTG) thermograms of PHB produced by *Rhodopseudomonas* sp. S16-VOGS3.

Table 2. Thermal properties of PHB produced by cultivation of purple bacteria.

| Microorganism | Biopolymer | T_c (°C) | T_g (°C) | T_m (°C) | ΔH_m (J/g) | x_c (%) | T (°C) | Ref. |
|---------------------------------------|------------|------------|------------|------------|--------------------|-----------|--------|------------|
| <i>Rhodopseudomonas</i> sp. S16-VOGS3 | PHB | 52.8 | 4.2 | 172 | 90.7 | 51 | 248 | This study |
| <i>Rhodococcus equi</i> | PHB | nd* | 2.8 | 173 | 74.5 | 62 | 276 | [30] |

nd*: not determined.

4. Conclusions

The main aim of the present work was to evaluate the performance of the novel tubular photobioreactor for producing PHB by outdoor cultivation of *Rhodospseudomonas* sp. S16-VOGS3 using lactate as carbon source. The results showed that the peculiar configuration of the photobioreactor permitted an optimal temperature control and solar light capturing for producing PHB-rich biomass. The reduction of the light intensity reduced the cumulative PHB showing the dominant role of this parameter. The thermal characterization of the recovered PHB showed a semi-amorphous polymer (51% crystallinity) with good thermal properties and stability, similar to those of PHBs obtained in other studies.

Author Contributions: P.C. conceived, designed and carried out the experiments; P.C., M.S. wrote the paper; P.C., M.S., P.C. discussed the data; N.M. performed the thermal characterizations of the recovered PHBs; A.L. contributed materials and analysis tools.

Funding: This research was funded by Tuscany Region with the Project “PHA”—POR FESR 2014–2020 (Bando 2–RSI 2014) grant number 3389.30072014.068000241 and the Project “PROSEV”, Fondo Europeo Agricolo per lo Sviluppo Rurale (FEASR), Asse Leader Piano di Sviluppo Rurale 2007 to 2013, Tuscany Region—Misura 124-Bando.

Acknowledgments: The authors would like to thank Giulia Padovani and Miriam Baldini (CNR-ISE) for their support in photobioreactor management and for carrying out the biomass analysis. We would also like to thank Daniele Grifone for sunlight data and Francesco Sabatini for the measurement of radiation spectrum (CNR-IBIMET).

Conflicts of Interest: The authors declare no conflict of interest.

References

1. COM (2018) 28. A European Strategy for Plastics in a Circular Economy. Available online: <http://ec.europa.eu/environment/circular-economy/pdf/plastics-strategy.pdf> (accessed on 2 September 2018).
2. Valavanidis, A. Global Plastic Waste and Oceans Pollution Million Tons of Plastic Waste have Gone Missing in the World Oceans? Athens, Greece, May 2016. Available online: <https://www.researchgate.net/publication/303549578> (accessed on 26 July 2018).
3. Jambeck, J.R.; Geyer, R.; Wilcox, C.; Siegler, T.R.; Perryman, M.; Andrady, A.; Narayan, R.; Law, K.L. Plastic waste inputs from land into the ocean. *Science* **2015**, *347*, 768–771. [[CrossRef](#)] [[PubMed](#)]
4. Bioplastics Market Data 2017. Global Production Capacities of Bioplastics 2017–2022. REPORT European Bioplastics. Available online: <https://www.european-bioplastics.org/market/> (accessed on 26 July 2018).
5. Balaji, S.; Gopi, K.; Muthuvelan, B. A review on production of poly β -hydroxybutyrate from cyanobacteria for the production of bio plastics. *Algal Res.* **2013**, *2*, 278–285. [[CrossRef](#)]
6. Carpine, R.; Olivieri, G.; Hellingwerf, K.; Pollio, A.; Marzocchella, A. The cyanobacterial route to produce poly- β -hydroxybutyrate. *Chem. Eng. Trans.* **2015**, *43*, 289–294. [[CrossRef](#)]
7. Padovani, G.; Carlozzi, P.; Seggiani, M.; Cinelli, P.; Vitolo, S.; Lazzeri, A. PHB-rich biomass and bioH₂ production by means of photosynthetic microorganisms. *Chem. Eng. Trans.* **2016**, *49*, 55–60. [[CrossRef](#)]
8. Rydz, J.; Sikorska, W.; Kyulavska, M.; Christova, D. Polyester-based (bio) degradable polymers as environmentally friendly materials for sustainable development. *Int. J. Mol. Sci.* **2015**, *16*, 564–596. [[CrossRef](#)] [[PubMed](#)]
9. Bugnicourt, E.; Cinelli, P.; Lazzeri, A.; Alvarez, V. Polyhydroxyalkanoate (PHA): Review of synthesis, characteristics, processing and potential applications in packaging. *Express Polym. Lett.* **2014**, *8*, 791–808. [[CrossRef](#)]
10. Mozumder, M.D.S.I.; Garcia-Gonzalez, L.; De Wever, H.; Volcke, E.I.P. Poly(3-hydroxybutyrate) (PHB) production from CO₂: Model development and process optimization. *Biochem. Eng. J.* **2015**, *98*, 107–116. [[CrossRef](#)]
11. Jiang, G.; Hill, D.J.; Kowalczyk, M.; Johnston, B.; Adamus, G.; Irorere, V.; Iza Radecka, I. Carbon sources for polyhydroxyalkanoates and an integrated biorefinery. *Int. J. Mol. Sci.* **2016**, *17*, 1157. [[CrossRef](#)] [[PubMed](#)]

12. Suzuki, T.; Tsygankov, A.; Miyake, J.; Tokiwa, Y.; Asa-da, Y. Accumulation of poly-(hydroxybutyrate) by a non-sulfur photosynthetic bacterium, *Rhodobacter sphaeroides* RV at different pH. *Biotechnol. Lett.* **1995**, *17*, 395–400. [[CrossRef](#)]
13. Khatipov, E.; Miyake, M.; Miyake, J.; Asada, Y. Accumulation of poly- β -hydroxybutyrate by *Rhodobacter sphaeroides* on various carbon and nitrogen substrates. *FEMS Microbiol. Lett.* **1998**, *162*, 39–45. [[CrossRef](#)]
14. Kim, B.W.; Chang, K.P.; Chang, H.N. Effect of light source on the microbiological desulfurization in a photobioreactor. *Bioprocess. Eng.* **1997**, *17*, 343–348. [[CrossRef](#)]
15. Padovani, G.; Emiliani, G.; Giovanelli, A.; Traversi, M.L.; Carlozzi, P. Assessment of glycerol usage by five different purple non-sulfur bacterial strains for bioplastic production. *J. Environ. Chem. Eng.* **2018**, *6*, 616–622. [[CrossRef](#)]
16. Carlozzi, P.; Sacchi, A. Biomass production and studies on *Rhodospseudomonas palustris* grown in an outdoor, temperature controlled, underwater tubular photobioreactor. *J. Biotechnol.* **2001**, *88*, 239–249. [[CrossRef](#)]
17. Carlozzi, P.; Pushparaj, B.; Degl'Innocenti, A.; Capperucci, A. Growth characteristics of *Rhodospseudomonas palustris* cultured outdoors, in an underwater tubular photobioreactor and investigation on photosynthetic efficiency. *Appl. Microbiol. Biot.* **2006**, *73*, 789–795. [[CrossRef](#)] [[PubMed](#)]
18. Al-Kaddo, K.B.; Sudesh, K.; Samian, M.R. Screening of bacteria for PHA production using waste glycerol as carbon source and the ability of new strain to produce P(3HB-co-3HV) copolymer. *Malaysian J. Microbiol.* **2016**, *12*, 245–253. [[CrossRef](#)]
19. Padovani, G.; Vaičiulytė, S.; Carlozzi, P. BioH₂ photoproduction by means of *Rhodospseudomonas palustris* sp. cultured in a lab-scale photobioreactor operated in batch, fed-batch and semi-continuous modes. *Fuel* **2016**, *166*, 203–210. [[CrossRef](#)]
20. Arrieta, M.P.; Samper, M.D.; Lopez, J.; Jiménez, A. Combined Effect of Poly(hydroxybutyrate) and Plasticizers on Polylactic acid Properties for Film Intended for Food Packaging. *J. Polym. Environ.* **2014**, *22*, 460–470. [[CrossRef](#)]
21. Carlozzi, P. Dilution of solar radiation through “culture” lamination in photobioreactor rows facing south north: A way to improve the efficiency of light utilization by cyanobacteria (*Arthrospira platensis*). *Biotechnol. Bioeng.* **2003**, *81*, 305–315. [[CrossRef](#)] [[PubMed](#)]
22. Hai, T.; Ahlers, H.; Gorenflo, V.; Steinbüchel, A. Axenic cultivation of anoxygenic phototrophic bacteria, cyanobacteria, and microalgae in a new closed tubular glass photobioreactor. *Appl. Microbiol. Biot.* **2000**, *53*, 383–389. [[CrossRef](#)]
23. Palamae, S.; Choerit, W.; Dechatiwongse, P.; Zhang, D.; del Rio-Chanona, E.A.; Chisti, Y. Production of renewable biohydrogen by *Rhodobacter sphaeroides* S10: A comparison of photobioreactors. *J. Clean Prod.* **2018**, *181*, 318–328. [[CrossRef](#)]
24. Watanabe, Y.; Saiki, H. Development of a photobioreactor incorporating *Chlorella* sp. for removal of CO₂ in Stack gas. *Energy Convers. Manag.* **1997**, *38*, 499–503. [[CrossRef](#)]
25. Khanna, S.; Srivastava, A.K. Optimization of nutrient feed concentration and addition time for production of poly(β -hydroxybutyrate). *Enzyme Microb. Tech.* **2006**, *39*, 1145–1151. [[CrossRef](#)]
26. Wang, Y.J.; Hua, F.L.; Tsang, Y.F.; Chan, S.Y.; Sin, S.N.; Chua, H.; Yu, P.H.F.; Ren, N.Q. Synthesis of PHAs from wastes under various C:N ratios. *Bioresour. Technol.* **2007**, *98*, 1690–1693. [[CrossRef](#)] [[PubMed](#)]
27. Johnson, K.; Kleerebezem, R.; van Loosdrecht, M.C.M. Influence of the C/N ratio on the performance of polyhydroxybutyrate (PHB) producing sequencing batch reactors at short SRTs. *Water Res.* **2010**, *44*, 2141–2152. [[CrossRef](#)] [[PubMed](#)]
28. Ahn, J.; Jho, E.H.; Nam, K. Effect of C/N ratio on polyhydroxyalkanoates (PHA) accumulation by *Cupriavidus necator* and its implication on the use of rice straw hydrolysates. *Environ. Eng. Res.* **2015**, *20*, 246–253. [[CrossRef](#)]
29. Carpine, R.; Raganati, F.; Olivieri, G.; Hellingwerf, K.J.; Pollio, A.; Salatino, P.; Marzocchella, A. Poly- β -hydroxybutyrate (PHB) production by *Synechocystis* PCC6803 from CO₂: Model development. *Algal Res.* **2018**, *29*, 49–60. [[CrossRef](#)]
30. Martino, L.; Cruz, M.V.; Scoma, A.; Freitas, F.; Bertin, L.; Scandola, M.; Reis, M.A.M. Recovery of amorphous polyhydroxybutyrate granules from *Cupriavidus necator* cells grown on used cooking oil. *Int. J. Biol. Macromol.* **2014**, *71*, 117–123. [[CrossRef](#)] [[PubMed](#)]

31. Altaee, N.; Fahdila, A.; Yousif, E.; Sudesh, K. Recovery and subsequent characterization of polyhydroxybutyrate from *Rhodococcus equi* cells grown on crude palm kernel oil. *J. Taibah Univ. Sci.* **2016**, *10*, 543–550. [[CrossRef](#)]
32. Sindhu, R.; Ammu, B.; Binod, P.; Deepthi, S.K.; Ramachandran, K.B.; Soccol, C.R.; Pandey, A. Production and characterization of poly-3-hydroxybutyrate from crude glycerol by *Bacillus sphaericus* NII 0838 and improving its thermal properties by blending with other polymers. *Braz. Arch. Biol. Technol.* **2011**, *54*, 783–794. [[CrossRef](#)]



© 2018 by the authors. Licensee MDPI, Basel, Switzerland. This article is an open access article distributed under the terms and conditions of the Creative Commons Attribution (CC BY) license (<http://creativecommons.org/licenses/by/4.0/>).