

Supplementary data

Waterborne acrylate-based hybrid coatings with enhanced resistance properties on stone surfaces

Francesca Sbardella ^{1,2,*}, Lucilla Pronti ³, Maria Laura Santarelli ¹, José María Asua González ², and Maria Paola Bracciale ^{1,*}

¹ Department of Chemical Engineering Materials Environment (DICMA) and Research Center in Science and Technology for the Preservation of Historical-architectural Heritage (CISTeC), Sapienza University of Rome, V. Eudossiana 18, 00184 Rome, Italy; marialaura.santarelli@uniroma1.it

² Department of Applied Chemistry, University of the Basque Country, (UPV/EHU), Avenida de Tolosa 723, 20018 Donostia-San Sebastián, Spain; jm.asua@ehu.es

³ Department of Basic and Applied Sciences for Engineering (SBAI), Sapienza University of Rome, V. Antonio Scarpa 14/16, 00161 Rome, Italy; luquilla.pronti@uniroma1.it

* Correspondence: francesca.sbardella@uniroma1.it (F.S.); mariapaola.bracciale@uniroma1.it (M.P.B.)

Error! Bookmark not defined.

Table S1. Values of the colorimetric measurements.

Sample	Nonaged				Aged				ΔE	ΔC
	L	a	b	C	L	a	b	C		
Reference	77.77	-1.05	-1.92	2.18	-	-	-	-	-	-
NoSiO ₂	64.68	-0.85	-1.60	1.81	74.41	-1.38	-1.69	2.18	9.74	0.54
L2_1	78.74	-1.06	-1.92	2.19	77.15	-1.37	-1.42	1.97	1.69	0.59
L2_2	75.85	-1.06	-2.82	3.01	73.94	-1.42	-1.43	2.02	2.39	1.44
L5_1	75.48	-1.24	-2.42	2.72	73.27	-1.61	-1.06	1.93	2.62	1.41
L5_2	75.19	-1.23	-2.13	2.46	73.65	-1.52	-1.86	2.41	1.58	0.40
L10_1	72.13	-1.14	-2.70	2.93	71.06	-1.90	0.26	1.92	3.24	3.06
L10_2	73.54	-1.04	-2.77	2.96	70.20	-2.26	1.73	2.84	5.73	4.66

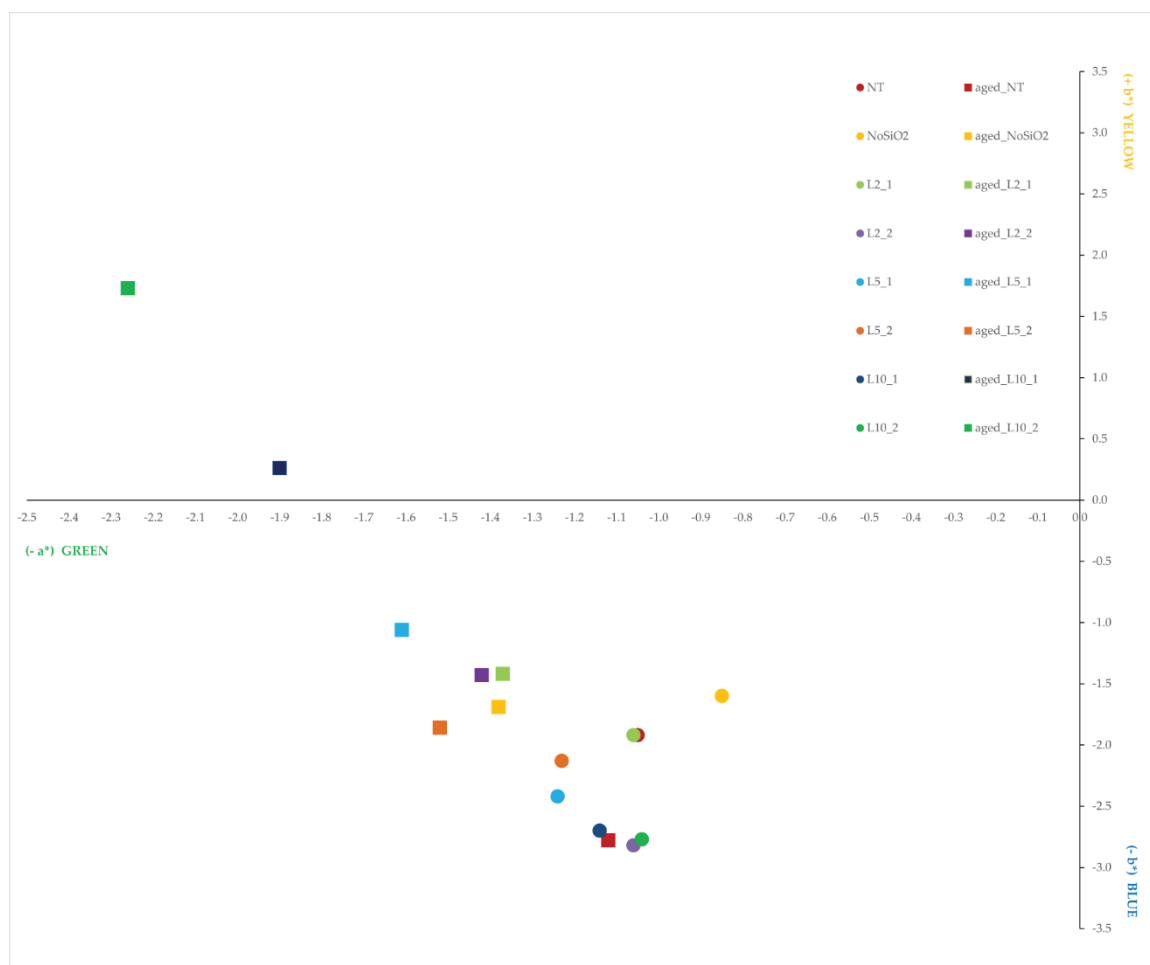


Figure S1. CIELaB measurements of the UV-irradiated latexes.